

On the nature of superconductivity in the t-J model of high- T_c superconductors

Th.A. Maier¹

¹*Computer Science and Mathematics Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831-6114*
(Dated: February 2, 2008)

Using an extended dynamical cluster approximation we study superconductivity in the two-dimensional t-J model. In analogy to the extended dynamical mean field theory, non-local spin fluctuations are treated self-consistently with an additional Bosonic bath. To solve the effective cluster problem, we employ an extended non-crossing approximation which allows for transitions to the symmetry-broken state. At sufficiently low temperatures we find a stable superconducting solution with d-wave order parameter. Upon pairing, the exchange energy is lowered, consistent with an exchange-based pairing mechanism.

Introduction. The nature of pairing in high-temperature superconductors (HTSC) remains one of the most outstanding open problems in materials science. After years of active research, we are still far from a complete theoretical understanding of the rich physics observed in these materials. Early in the history of HTSC it was realized that electronic correlations play a crucial role not only for the pairing-mechanism in HTSC but also for their unusual normal state behavior [1]. Hence, models describing the behavior of itinerant correlated electrons, in particular the Hubbard model and its strong-coupling limit, the t-J model, were proposed to capture the generic physics of HTSC [2, 3]. However, despite intensive studies, these models remain unsolved in two dimensions.

Conventional (BCS) superconductors are well understood. Electrons can lower their potential energy by forming Cooper-pairs. Chester [4] realized that this reduction in the electronic potential energy actually corresponds to a decrease in the ionic kinetic energy, thus providing a clear link between the pairing mechanism and the lattice degrees of freedom. In analogy to Chester's idea, Scalapino and White [5] suggested an analogous relation for the origin of the pairing energy in HTSC based on numerical calculations for the t-J model. They proposed, if spin correlations are involved in the pairing mechanism, that the condensation energy in HTSC is provided by the exchange energy $J \sum_{\langle ij \rangle} \langle \vec{S}_i \cdot \vec{S}_j \rangle$. Consistent with this idea, neutron scattering experiments in HTSC have shown the evolution of a low-energy spin-fluctuation resonance in the superconducting state, which can be related to a reduction in exchange energy [6, 7].

This analogy to conventional BCS superconductors however, has recently been contrasted by optical experiments in BSCCO [8]. While in BCS superconductors the kinetic energy slightly increases upon pairing, these experiments have shown that pairing in HTSC occurs through a reduction of the electronic kinetic energy. In order to unify these two seemingly controversial observations, it is important to note that in the t-J model, magnetic exchange has mixed electronic kinetic and Coulom-

bic origins. In addition, even the kinetic term in the t-J Hamiltonian has Coulombic contributions due to the restriction of no double-occupancy of a given site. Thus, while the Hubbard model with its purely kinetic and Coulombic terms can be related to the optical experiments, the t-J model has a well defined exchange energy and hence is the model of choice to study the possibility of exchange based pairing.

Using QMC simulations within the dynamical cluster approximation (DCA), we have shown that pairing in the 2D Hubbard model indeed happens through a reduction of the electronic kinetic energy [9], consistent with the experimental observation. To explore the possibility of exchange-based pairing, we study in this letter the nature of superconductivity in the 2D t-J model. Its Hamiltonian reads in usual notation

$$H = -t \sum_{\langle ij \rangle, \sigma} \tilde{c}_{i\sigma}^\dagger \tilde{c}_{j\sigma} + J \sum_{\langle ij \rangle} (\vec{S}_i \cdot \vec{S}_j - \frac{1}{4} n_i n_j), \quad (1)$$

where the projected operators $\tilde{c}_{i\sigma}, \tilde{c}_{i\sigma}^\dagger$ act in the reduced Hilbert-space with empty and doubly occupied sites only and $n_i = \sum_{\sigma} \tilde{c}_{i\sigma}^\dagger \tilde{c}_{i\sigma}$ are their corresponding number operators. Unless otherwise noted, we use the hopping integral t for the energy scale and set $J = 0.3t$.

The possibility of $d_{x^2-y^2}$ pairing in the 2D t-J model was indicated in a number of numerical studies of finite size systems (for a review see [10]). Only recent numerical calculations provided evidence for pairing in relatively large systems for physically relevant values of J/t [11, 12]. The question of whether pairing persists in the infinite size model however remains open. Thus, simulations for the thermodynamic limit are clearly desirable to further support the finite size results.

Simulations within the dynamical mean field theory (DMFT) take place in the thermodynamic limit. An extended DMFT (EDMFT) study of the pseudogap in the t-J model was presented in Ref. [13]. But the lack of non-local correlations in the DMFT method inhibits transitions to states with non-local order parameters such as d-wave superconductivity. The dynamical cluster approximation (DCA) extends the DMFT by mapping the original lattice model onto a periodic cluster with linear

size L_c embedded in a self-consistent host. As a result, dynamical correlations up to a range $\sim L_c$ are treated accurately while the longer-ranged physics is described on the mean-field level.

Method. A detailed discussion of the DCA for models with local interactions like the Hubbard model was given in Ref. [14, 15]. The first Brillouin zone is divided into $N_c = L_c^D$ cells where D is the dimension, with each cell represented by its center wave-vector, the cluster $\mathbf{K}$ -points. The reduction of the N -site lattice problem to an effective N_c -site cluster problem is achieved by coarse-graining the compact diagrams of the free energy, i.e. averaging over the N/N_c wave-vectors $\mathbf{k}$ within a cell. Consequently, the Feynman diagrams for the lattice self-energy collapse onto those of an effective cluster model embedded in a Fermionic host which accounts for all fluctuations arising from hopping of electrons between the cluster and the rest of the system.

In the following we outline the modifications necessary to treat models with non-local interactions like the t-J model. Since the projected operators $\tilde{c}_{i\sigma}$ in the t-J Hamiltonian (1) do not obey standard Fermionic commutation relations, the diagrammatic derivation of the DCA cannot be applied to the t-J model. However, the general idea of the DCA, i.e. the approximation of irreducible lattice quantities by their corresponding cluster quantities can still be applied to the t-J model. An extended algorithm for models, such as the t-J model, with extended range interactions was formulated in Ref. [15] for the DCA. For the cluster size $N_c = 1$ this algorithm corresponds to the extended DMFA (EDMFA) [16]. Fluctuations associated with the non-local interactions are accounted for by an additional Bosonic bath which reflects the influence of the host on the two-particle level. In the case of the t-J model, it represents the fluctuating magnetic fields induced by J .

In the DCA, the effective cluster model is conveniently represented in reciprocal cluster space

$$\begin{aligned}
H_{cl} = & \sum_{\mathbf{K}, \sigma} \bar{\epsilon}_{\mathbf{K}} \tilde{c}_{\mathbf{K}\sigma}^\dagger \tilde{c}_{\mathbf{K}\sigma} + \sum_{\mathbf{Q}} \left[\bar{J}_{\mathbf{Q}} \mathbf{S}_{\mathbf{Q}} \cdot \mathbf{S}_{-\mathbf{Q}} - \frac{1}{4} \rho_{\mathbf{Q}} \rho_{-\mathbf{Q}} \right] \\
& + \sum_{\mathbf{K}, \tilde{\mathbf{k}}, \sigma} \left[V_{\mathbf{K}, \tilde{\mathbf{k}}} \tilde{c}_{\mathbf{K}\sigma}^\dagger a_{\mathbf{K}+\tilde{\mathbf{k}}} + h.c. \right] \\
& + \sum_{\mathbf{Q}, \tilde{\mathbf{q}}} \left[I_{\mathbf{Q}, \tilde{\mathbf{q}}} \mathbf{S}_{\mathbf{Q}} \cdot (\Phi_{\mathbf{Q}+\tilde{\mathbf{q}}} + \Phi_{-\mathbf{Q}-\tilde{\mathbf{q}}}^\dagger) + h.c. \right] \\
& + \sum_{\mathbf{k}\sigma} \lambda_{\mathbf{k}} a_{\mathbf{k}\sigma}^\dagger a_{\mathbf{k}\sigma} + \sum_{\mathbf{q}} \omega_{\mathbf{q}} \Phi_{\mathbf{q}}^\dagger \cdot \Phi_{\mathbf{q}}. \quad (2)
\end{aligned}$$

The operators $\tilde{c}_{\mathbf{K}\sigma}^{(\dagger)}$ create (destroy) Fermions on the cluster with wave-vector $\mathbf{K}$ and $\mathbf{S}_{\mathbf{Q}}$ ($\rho_{\mathbf{Q}}$) are their corresponding spin- (density-) operators. The sums over $\tilde{\mathbf{k}}$ and $\tilde{\mathbf{q}}$ run over the momenta within a DCA cell about the cluster momenta $\mathbf{K}$ and $\mathbf{Q}$. In the DCA, non-local parameters are coarse-grained, i.e. $\bar{\epsilon}_{\mathbf{K}} = N_c/N \sum_{\tilde{\mathbf{k}}} \epsilon_{\mathbf{K}+\tilde{\mathbf{k}}}$

and $\bar{J}_{\mathbf{Q}} = N_c/N \sum_{\tilde{\mathbf{q}}} J_{\mathbf{Q}+\tilde{\mathbf{q}}}$ are given by the cell-averages of the lattice Fourier-transforms $\epsilon_{\mathbf{k}}$ and $J_{\mathbf{q}}$ of t and J . The Fermionic and Bosonic hosts are described by the auxiliary operators $a_{\mathbf{k}\sigma}^{(\dagger)}$ and $\Phi_{\mathbf{q}}^{(\dagger)}$ with corresponding energies $\lambda_{\mathbf{k}}$ and $\omega_{\mathbf{q}}$. When the system becomes superconducting, an additional U(1) symmetry breaking term

$$H_{SC} = \sum_{\mathbf{k}} \left[\Delta_{\mathbf{k}} a_{\mathbf{k}\downarrow}^\dagger a_{-\mathbf{k}\uparrow}^\dagger + h.c. \right] \quad (3)$$

has to be introduced to simulate the existence of paired states in the host.

The solution of the cluster problem given by $H_{cl} + H_{SC}$ yields the cluster Green function $\mathbf{G}_c(\mathbf{K}, \omega)$, cluster spin susceptibility $\chi_c(\mathbf{Q}, \omega)$ and their corresponding self-energies $\Sigma(\mathbf{K}, \omega)$ and $M(\mathbf{Q}, \omega)$. In the DCA, lattice self-energies are approximated by their corresponding cluster quantities, i.e. the lattice Green function is written as

$$\mathbf{G}(\mathbf{k}, \omega) = [\omega \tau_o - \epsilon_{\mathbf{K}+\tilde{\mathbf{k}}} \tau_3 - \Sigma(\mathbf{K}, \omega)]^{-1}. \quad (4)$$

To allow for the possibility of superconducting order we used the Nambu-Gorkov matrix representation [17] with Pauli-spin matrices τ_i . The 11-component of $\mathbf{G}$ is given by the normal single-electron Green function $G(\mathbf{k}, z) = \langle \langle c_{\mathbf{k}\uparrow}; c_{\mathbf{k}\uparrow}^\dagger \rangle \rangle_z$, while the 12-component is the anomalous Green function $F(\mathbf{k}, z) = \langle \langle c_{\mathbf{k}\uparrow}; c_{-\mathbf{k}\downarrow} \rangle \rangle_z$ and only finite in the superconducting state. The lattice spin susceptibility becomes

$$\chi(\mathbf{q}, \omega) = \frac{1}{M(\mathbf{Q}, \omega) + J_{\mathbf{q}}}. \quad (5)$$

Self-consistency is imposed by demanding that the cluster Green function $\mathbf{G}_c$ and spin-susceptibility χ_c are equal to the coarse grained, i.e. cell averaged lattice Green function

$$\begin{aligned}
\bar{\mathbf{G}}(\mathbf{K}, z) &= \frac{N_c}{N} \sum_{\tilde{\mathbf{k}}} \mathbf{G}(\mathbf{K} + \tilde{\mathbf{k}}, \omega) \\
&= [\omega \tau_o - \bar{\epsilon}_{\mathbf{K}} \tau_3 - \Sigma(\mathbf{K}, \omega) - \Gamma(\mathbf{K}, \omega)]^{-1} \quad (6)
\end{aligned}$$

and lattice spin-susceptibility

$$\begin{aligned}
\bar{\chi}(\mathbf{Q}, \omega) &= \frac{N_c}{N} \sum_{\tilde{\mathbf{q}}} \chi(\mathbf{Q} + \tilde{\mathbf{q}}, \omega) \\
&= \frac{1}{M(\mathbf{Q}, \omega) + \bar{J}(\mathbf{Q}) + \Theta(\mathbf{Q}, \omega)} \quad (7)
\end{aligned}$$

respectively, where the sums run over momenta within the DCA cell about the cluster momentum $\mathbf{K}$. The DCA self-consistent problem is then solved by iteration. In this procedure, the auxiliary parameters of the cluster model $\lambda_{\mathbf{k}}$, $\omega_{\mathbf{q}}$, $\Delta_{\mathbf{k}}$, $V_{\mathbf{K}, \tilde{\mathbf{k}}}$ and $I_{\mathbf{Q}, \tilde{\mathbf{q}}}$ are replaced by the hybridization functions $\Gamma(\mathbf{K}, \omega)$ and $\Theta(\mathbf{Q}, \omega)$ which are self-consistently determined from the coarse grained lattice quantities $\bar{\mathbf{G}}$, Eq. (6) and $\bar{\chi}$, Eq. (7). Hence, the

particular form of the auxiliary degrees of freedom in Eqs. (2) and (3) is irrelevant and thus does not impose any further approximation.

Although the complexity of the problem is highly reduced by the DCA, the solution of the effective quantum cluster problem remains non-trivial. The additional coupling to the Bosonic bath renders many traditional methods used to solve the purely Fermionic cluster model like e.g. QMC difficult to apply. Here we employ an extended version of the non-crossing approximation which is based on an infinite resummation of certain classes of diagrams in a perturbational expansion in the couplings to the Fermionic and Bosonic baths. A detailed derivation of the NCA equations for the EDMFT quantum impurity model ($N_c = 1$) was given in Ref.[18]. The application of the NCA to the Fermionic DCA cluster problem was discussed in Ref.[19] and the modifications necessary to treat the superconducting state in Ref.[20]. A detailed discussion of the NCA equations for the extended cluster problem embedded in the additional Bosonic bath will be presented elsewhere.

Results. We performed simulations for the cluster size $N_c = 4$, the smallest possible cluster size that can capture pairing with the d -wave order parameter in the t-J model. Thus, this theory should be regarded as the mean-field theory for d -wave superconductivity in the t-J model. In particular, we choose the conventional set of cluster $\mathbf{K}$ -points $\{(0,0), (\pi,0), (0,\pi), (\pi,\pi)\}$.

To show that our technique is indeed able to describe superconductivity within the t-J model, we present in Fig. 1 our results for the single-particle spectrum at 20% doping ($\delta = 0.20$) and temperature $T = 0.0348t$ below the superconducting phase transition at $T_c = 0.0377t$. The density of states $N(\omega)$ shown in Fig. 1A develops a pseudogap at the chemical potential ($\omega = 0$), when the anomalous Green-function $\bar{F}(\mathbf{K}, \omega) = \langle\langle \tilde{c}_{\mathbf{K}\uparrow}; \tilde{c}_{-\mathbf{K}\downarrow} \rangle\rangle$ shown in Fig. 1B, becomes finite. The $\mathbf{K}$ -dependence of the coarse-grained anomalous Green function, i.e. $\bar{F}((\pi,0), \omega) = -\bar{F}((0,\pi), \omega)$ and zero otherwise (not shown), is consistent with a $d_{x^2-y^2}$ -symmetry of the order parameter. Fig. 1C shows the doping dependence of the transition temperature. $T_c(\delta)$ has a maximum $T_c^{max} \approx 0.0377t \approx 110\text{K}$ (for $t = 0.25\text{eV}$) at the optimal doping $\delta \approx 0.20$ and decreases with both increasing and decreasing doping. Due to the breakdown of the NCA technique at very low temperatures, the phase-diagram cannot be extended beyond the region shown and in particular no prediction can be made for the critical doping beyond which superconductivity vanishes.

It is interesting to note that without the additional coupling to the Bosonic host we were not able to stabilize a superconducting solution, at least not above the lowest temperatures we can simulate with our technique. This shows the importance of a self-consistent treatment of the spin-fluctuations between the cluster and host.

To explore the nature of pairing in our simula-

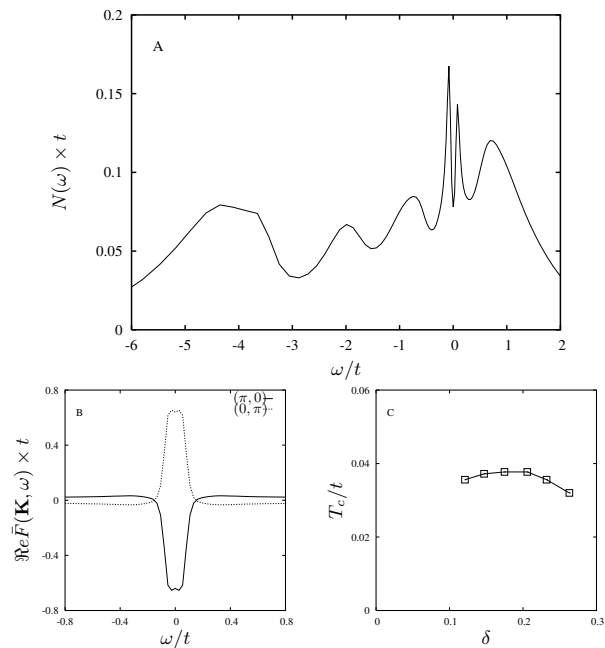


FIG. 1: (A) Density of states and (B) real part of the coarse-grained anomalous Green function in the superconducting state of the 2D t-J model at 20% doping at $T = 0.0348t$. (C) Doping dependence of the critical temperature T_c .

tions, we calculate the exchange energy E_{xc} from the spin-susceptibility $\chi(\mathbf{q}, \omega)$, Eq. (5), via the fluctuation-dissipation theorem as

$$\begin{aligned}
 E_{xc} &= \frac{1}{N} \sum_{\mathbf{q}} J(\mathbf{q}) \langle \vec{S}(\mathbf{q}) \cdot \vec{S}(-\mathbf{q}) \rangle \\
 &= -\frac{3}{\pi} \frac{1}{N} \sum_{\mathbf{q}} J(\mathbf{q}) \int d\omega \frac{\Im m \chi(\mathbf{q}, \omega)}{1 - e^{-\beta\omega}}. \quad (8)
 \end{aligned}$$

To obtain results for the normal state below the transition temperature T_c we suppress superconductivity by not allowing for a finite order parameter in our simulation.

The exchange energies in the normal and superconducting states as a function of temperature close to the critical temperature T_c at 20% doping are shown in Fig. 2. Our results for the nature of pairing in the 2D t-J model are consistent with an exchange-based pairing mechanism: Below T_c , the exchange energy in the superconducting state is reduced compared to the normal state, while the energy coming from the kinetic (first) term in the t-J model, Eq. (1), slightly increases upon pairing (not shown). It is important to remember that in the mapping of the Hubbard model to the t-J model, the exchange interaction J comes from virtual hopping processes between neighboring sites and thus has kinetic character. Hence the present results are consistent with our results for the Hubbard model where we found the superconducting instability to be accompanied by a lowering of

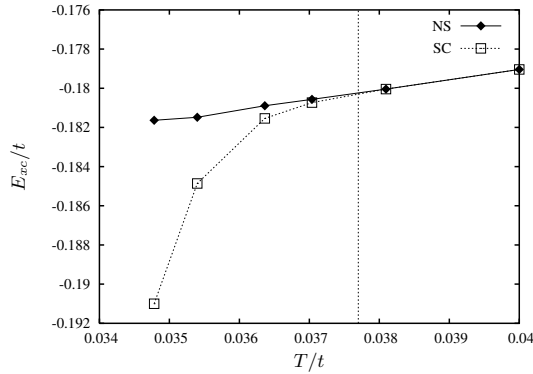


FIG. 2: Exchange energy as a function of temperature at 20% doping across the superconducting transition in the normal (NS) and superconducting (SC) states.

the electronic kinetic energy [9]. The nature of pairing in the t-J model however is more similar to that in BCS superconductors: The energy of the exchange coupling which plays a similar role to that of the lattice degrees of freedom in BCS superconductors, is reduced.

Neutron scattering experiments relate the gain in exchange energy to the development of a resonance in the spin-susceptibility near $\mathbf{Q} = (\pi, \pi)$ and 40 meV. According to Eq. (8), the exchange energy E_{xc} is reduced when the spectral weight in the spin-susceptibility $\chi(\mathbf{q}, \omega)$ is increased near $\mathbf{q} = (\pi, \pi)$ since $J(\mathbf{q}) = J(\cos q_x + \cos q_y) < 0$ in this region in $\mathbf{q}$ -space. In Fig. 3 we plot the imaginary part of the dynamic coarse-grained spin-susceptibility at $\mathbf{Q} = (\pi, \pi)$ in the normal and superconducting states at 20% doping for two different temperatures below the critical temperature T_c . This $\mathbf{q}$ -space averaged quantity allows us to infer the changes in spectral weight which according to Eq. (8) reduce the exchange energy. Although our data does not display the develop-

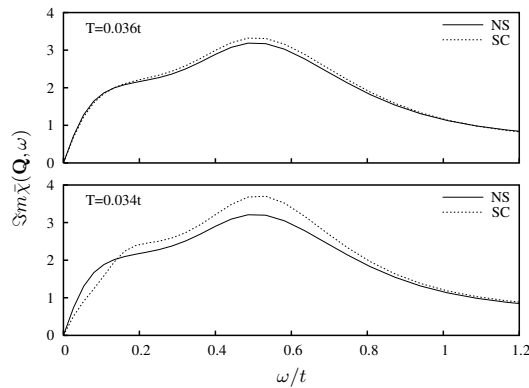


FIG. 3: Imaginary part of the coarse-grained dynamic spin-susceptibility in the 2D t-J model for $\mathbf{Q} = (\pi, \pi)$ at $T=0.036t$ (top) and $T=0.034t$ (bottom) in the superconducting (SC) and normal (NS) states.

ment of the narrow resonance peak at ~ 40 meV observed

in experiments, we find that the reduction in exchange energy indeed originates in an increase of spectral weight in $\chi_s(\mathbf{q}, \omega)$ in the region near $\mathbf{Q} = (\pi, \pi)$ consistent with experiments.

To summarize, we have presented extended DCA/NCA simulations for the 2D t-J model which show evidence for a *d*-wave superconducting state in the thermodynamic limit. We find that the pairing instability is accompanied by a reduction of the exchange energy consistent with exchange-based pairing. In agreement with neutron scattering experiments, this exchange energy reduction originates in an increase in the magnetic response around the antiferromagnetic wave-vector $\mathbf{Q} = (\pi, \pi)$.

Acknowledgements It is a pleasure to acknowledge useful discussions with M. Jarrell, T. Pruschke and M. Vojta. Research performed as a Eugene P. Wigner Fellow and staff member at the Oak Ridge National Laboratory, managed by UT-Battelle, LLC, for the U.S. Department of Energy under Contract DE-AC05-00OR22725.

-
- [1] P. W. Anderson, *The Theory of Superconductivity in the High- T_c Cuprates* (Princeton University Press, Princeton, NJ, 1997).
 - [2] P. W. Anderson, *Science* **235**, 1196 (1987).
 - [3] F. Zhang and T. Rice, *Phys. Rev. B* **37**, 3759 (1988).
 - [4] G. Chester, *Phys. Rev.* **103**, 1693 (1956).
 - [5] D. Scalapino and S. White, *Phys. Rev. B* **58**, 8222 (1998).
 - [6] E. Demler and S. Zhang, *Nature* **396**, 733 (1998).
 - [7] P. Dai, H. Mook, S. Hayden, G. Aeppli, T. Perring, R. Hunt, and F. Dogan, *Science* **284**, 1344 (1999).
 - [8] H. J. A. Molegraaf, C. Presura, D. van der Marel, P. H. Kes, and M. Li, *Science* **295**, 2239 (2002).
 - [9] T. Maier, M. Jarrell, A. Macridin, and C. Slezak, to appear in *Phys. Rev. Lett.* (2003).
 - [10] E. Dagotto, *Rev. Mod. Phys.* **66**, 763 (1994).
 - [11] S. Sorella, G. Martins, F. Becca, C. Gazza, L. Capriotti, A. Parola, and E. Dagotto, *Phys. Rev. Lett.* **88**, 117002 (2002).
 - [12] D. Poilblanc and D. Scalapino, preprint cond-mat/0202180 (2002).
 - [13] K. Haule, A. Rosch, J. Kroha, and P. Wölfle, *Phys. Rev. Lett.* **89**, 236402 (2002).
 - [14] M. H. Hettler, A. N. Tahvildar-Zadeh, M. Jarrell, T. Pruschke, and H. R. Krishnamurthy, *Phys. Rev. B* **58**, R7475 (1998).
 - [15] M. H. Hettler, M. Mukherjee, M. Jarrell, and H. R. Krishnamurthy, *Phys. Rev. B* **61**, 12739 (2000).
 - [16] J. Smith and Q. Si, *Phys. Rev. B* **61**, 5184 (2000).
 - [17] J. Schrieffer, *Theory of superconductivity* (Addison Wesley, Reading, MA, 1993).
 - [18] K. Haule, A. Rosch, J. Kroha, and P. Wölfle, preprint cond-mat/0304096 (2003).
 - [19] T. Maier, M. Jarrell, T. Pruschke, and J. Keller, *Eur. Phys. J B* **13**, 613 (2000).
 - [20] T. Maier, *Nonlocal Dynamical Correlations in Strongly Interacting Fermion Systems* (Logos Verlag Berlin, Berlin, Germany, 2001).